

Using cross-polarised photography as a guide for selecting resin composite shade

Carlos Andres Villavicencio-Espinoza¹, Mayara Hana Narimatsu² and Adilson Y Furuse³

Discoloured teeth are classic problems that impair the aesthetics of anterior teeth. When affecting multiple teeth, systemic aetiologies are usually associated, and ceramic veneers are good treatment options (Furuse et al, 2016).

On the other hand, a single discoloured tooth is often related to root canal treatment (Barber and King, 2014a), and severely discoloured teeth require the combination of walking bleach and external whitening treatments for the bleaching to be more effective (Barber and King, 2014b).

However, a major problem is the recurrence of discolouration. In this case, the aesthetic solution is frequently to cover the discoloured tooth with dental crowns or veneers.

While crowns should be precisely indicated to avoid unnecessary dental preparation (Prevedello et al, 2012), more conservative treatments, such as indirect and direct veneers, have become alternatives for patients with aesthetic problems with their anterior teeth (Fahl, 2006; Gomes and Perdigao, 2014; Korkut et al, 2013).

Direct veneer resin composites associated with adhesive systems have shown good mechanical properties and colour stability, as well as excellent aesthetic results (Ferracane, 2011). The current assortments of resin composites with different hues, chromas, and values make it possible to use the layering technique to create restorations that are indistinguishable from the natural dentition (Reis et al, 2009).

However, one of the greatest challenges when employing resin composites for veneering single discoloured teeth is the shade selection of natural teeth. Although some methods have been suggested in the literature, the success is considered subjective and highly dependent on the clinical experience of the operator (Haddad et al, 2011; Paolone et al, 2014).

Different alternatives have been developed to facilitate the colour selection, such as the use of spectrophotometers or colorimeters (devices for colour measurement).

However, these devices have some disadvantages related to high cost. Moreover, sometimes the device does not properly indicate the correct colour, or the selected shade may not be compatible with the resin composite to be used (Bahannan, 2014; Zenthofer et al, 2014).

An interesting approach that can be very helpful for selecting the shade of resin composites is the use of polarising filters associated with digital photography, known as cross-polarised photography (Fleming et al, 1989).

This technique uses two linear polarising filters: one in front of the lens and the other in front of the flash (light source).

If the two filters are placed in the same plane of polarisation, they are parallel and do not eliminate all reflections. However, when one of the filters is rotated 90 degrees to the other, providing crossed planes of polarisation, near-to-zero light interference is produced, and the clinician can then observe the teeth in a new way, without reflections (Fleming et al, 1989; Kim et al, 2012; Pekarek, 1993).

¹Carlos Andres Villavicencio-Espinoza DDS MS PhD
Department of Operative Dentistry, Endodontics, and Dental Materials, Bauru School of Dentistry, University of Sao Paulo, Brazil.

²Mayara Hana Narimatsu DDS MS
Department of Operative Dentistry, Endodontics, and Dental Materials, Bauru School of Dentistry, University of Sao Paulo, Brazil.

³Adilson Y Furuse DDS MS PhD
Department of Operative Dentistry, Endodontics, and Dental Materials, Bauru School of Dentistry, University of Sao Paulo, Brazil.



Figure 1: Preoperative frontal view showing a discolouration on maxillary right central incisor.



Figure 3: Initial colour of the discoloured tooth evaluated with cross-polarisation imaging. An A4 shade was observed with a Vita shade guide.

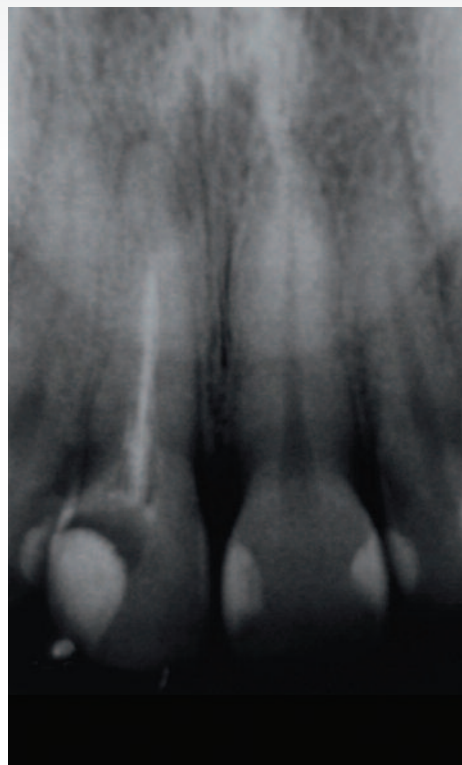


Figure 2: - Radiographic evaluation revealed an inadequate endodontic treatment with an alteration in the periapical area.

The advantage of this technique is that it allows a better understanding of the depth, details, characteristics, and transparencies of the dental structure. Additionally, the characteristics of the underlying dentine can be evaluated. In other words, this technique enables easier and straightforward appreciation of colour.

The purpose of this case report is to describe a step-by-step clinical case in which the patient had a discoloured maxillary anterior tooth restored with a resin composite veneer.

The use of cross-polarised photography for choosing dentine, enamel, and incisal shade is described.

Clinical report

A 30-year-old female patient was referred for treatment, complaining about the aesthetic appearance of her maxillary right central incisor. The clinical evaluation showed a single discoloured tooth and unsatisfactory old resin composite restorations (Figure 1).

The main cause of the discolouration was attributed to

endodontic treatment. No sensitivities to percussion were detected horizontally or vertically. However, radiographic evaluation revealed inadequate endodontic treatment with an alteration in the periapical area (Figure 2).



Figure 4: Different setups for obtaining cross-polarised photography. Left: a single flash with a polarised niter on the camera. Right: a twin flash using two polarising niters. Both options always had a polarised niter adapted in front of the lens



Figure 5: Final appearances after bleaching treatment.



Figure 6: Evaluation of the shade of the sound central incisor with cross-polarised photography. It is possible to note an A1 shade for the dentine.

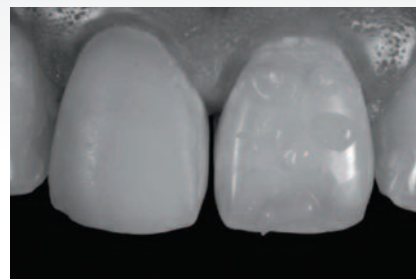


Figure 7: Greyscale photography used for evaluation of value of the resin composites to be used in the stratincation.



Figure 8: Cross-polarised photography used for evaluation of the shade of the resin composites to be used in the stratincation.

The treatment plan included the following phases:

1. Root canal retreatment, a non-vital tooth bleaching using a combination of walking bleach and in-office bleaching techniques
2. Cementation of a fibre-reinforced post and a resin composite buildup on the palatal surface
3. Direct resin composite veneer.

Phase one

After root canal retreatment, the initial shade of the discoloured tooth was selected using cross-polarised photography and a Vita Classic shade guide (Vita, Vita Zahnfabrik). An A4 darkened tooth shade was observed (Figure 3). In contrast, the natural shade of the patient's teeth was B1.

For cross-polarised photography, polarising filters were adapted to both a Sigma macro 105mm lens attached to an SLR Nikon D5300 camera and the built-in flash in a way that the filters were rotated 90 degrees to one another to provide crossed planes of polarisation.

The camera was adjusted in manual mode to f/11,

1/100, and ISO 400. Figure 4 shows different setups for obtaining cross-polarised photography.

After rubber dam isolation, removal of coronal endodontic sealer until 1 mm apical to the cemento-enamel junction, and resealing of the obturated canal with a glass ionomer cement (Vidrion R, 55 White), the walking bleach agent was prepared with a mixture carbamide peroxide and glycerin.

This bleaching agent was applied to the pulp chamber, and a temporary restorative material was used (Coltosol F, Coltene).

The walking bleach product was replaced every seven days for three weeks. In the third week, external/internal in-office bleaching was applied only on the affected tooth.

Phase two

Two weeks after bleaching, a post space was prepared, a fibre-reinforced post (Whitepost DC-E, FGM) was cemented using a self-adhesive resin cement (U200, 3M Espe), and a resin composite reconstruction of the palatal surface was made with 81 dentine and enamel shades (Opallis, FGM).

This selection of shades was based on the colour of the sound teeth and was made to avoid any possible decrease on brightness due to the thickness of the remaining facial dentine.

Phase three

The final post-bleaching shade of the maxillary right central incisor was evaluated, and A 1 was selected. Cross-polarised photography and a Vita Classic shade guide were used as previously described. The conventional shade selection of the sound maxillary left central incisor using a Vita Classic shade guide showed a 81 shade (Figure 5).

Wave-shaped white bands could be detected in the



Figure 9: Dental preparation finished.



Figure 10: An opaque flowable resin composite was applied over the discoloured dentine substrate to match the value of the natural tooth.



Figure 11: A3 dentine shade applied in cervical and middle thirds and A2 dentine shade applied in middle and incisal areas.

cervical and middle thirds, while an opalescence effect was observed at the incisal third. With cross-polarised photography, it was possible to observe that the dentine of the sound maxillary left central incisor had an A1 shade (Figure 6).

The shade selection for the resin composite was made on the sound central incisor. Small portions of resin composites were applied and light activated on the tooth's facial surface. During the shade selection, greyscale and cross-polarised pictures were taken (Figures 7 and 8). The greyscale picture was taken to evaluate the value of the resin composite to be used. These photographs were also used as a reference in the stratification of the final restoration.

Afterward, modified rubber dam isolation and the silhouette technique were used for tooth preparation. A round #1014 diamond bur (KG Sorensen) was used at high speed under water cooling to create cervical and proximal grooves. A tapered, round-ended #2135 diamond bur (KG Sorensen) was used for preparing vertical grooves and reducing the incisal edge. These grooves were used as depth cuts to facilitate the facial and incisal reduction of the veneer preparation.

In order to facilitate the cervical finishing, a #000 retraction cord (Ultradent) was used for gingival displacement (Figure 9). The tooth was etched with 35% phosphoric acid for 15 seconds. After rinsing with water, an adhesive (Ambar, FGM) was applied and light activated according to the manufacturer's guidelines.

Initially, an opaque white flowable resin composite (Kolor Plus, Kerr) was applied over the discoloured dentine substrate to match the value of the patient's natural tooth (Figure 10).

After this step, a thin layer of an opaque resin composite (OP, Opallis) was applied.

Afterward, a small layer of dentine shade (A3, Opallis) was applied to the cervical and middle thirds, and the dentine shade (A2, Opallis) was placed in the middle and incisal areas (Figure 11). These two procedures were performed separately, and both increments were light activated for 40 seconds.

Before adding the enamel layer, the intrinsic characteristics and highintensity hue of the adjacent teeth were accomplished with the aid of tints (Kolor Plus). In this stage, a white stain was used to reproduce wave-shaped bands in the cervical and middle thirds, and a blue stain was applied between dentine lobes to create an opalescence-like bluish effect at the incisal third.

All tints were applied with a thin brush (Figure 12). The last layer of artificial enamel was made with B1 enamel shade (EB1, Opallis) for the cervical third and bleached enamel shade (E-Bleach, Opallis) for the middle and incisal thirds. The two portions of resin composite were applied from the cervical to incisal area with a flat spatula to completely cover the underlying resin layers in one step (Figure 13). The facial surface was light activated for 40 seconds.

After the restoration was completed, finishing was accomplished with a #12 surgical blade (Lamedid) to remove resin composite excess in the cervical area. A pencil was used to highlight line angles of both central incisors, and a caliper was used to analyse light-reflecting areas (Figure 14). Sharp transitions between line angles were softened with a coarse finishing disc (TDV).

The restoration was polished with a sequence of polishing discs from coarse to superfine (TDV) and a silicone disc (TDV). The final polishing was accomplished with a felt disc and a 40-1 m diamond-based paste (TDV). The final restoration can be observed in Figure 15.



Figure 12: Colour characteristics were established using white stain in cervical and middle areas to reproduce wave-shaped bands. A blue stain was applied between dentine lobes to obtain an opalescence effect at the incisal third.



Figure 13: Application of the enamel layer.



Figure 15: Two-month follow-up showing the final result of the restored tooth.



Figure 14: A pencil was used to highlight the line angles, and a caliper was used to check the symmetry between central incisors. Blue stain was applied between dentine lobes to obtain an opalescence effect at the incisal third.

Discussion

The presented clinical situation reports an approach to a common problem when restoring maxillary anterior teeth and how to evaluate the inner characteristics of the dentine.

While dentine has a role in the reflection and absorption of light, being responsible primarily for the shades of natural teeth and saturation, enamel is rich in minerals and behaves like a translucent glass-like object that allows light to pass through it (Uoiner, 2004). This phenomenon results in light dispersion and scattering.

Other determining factors of a successful restoration include the tooth shape, surface characterisation, and propagation of light inside the restoration (Vanini, 1996). As demonstrated in the present case report, these last factors can be more easily observed and corrected using a pencil to highlight line angles of both central incisors and a caliper to analyse light-reflecting areas.

Shade selection of natural teeth is a complex process

because it involves subjective factors that depend directly on the observer, light source, and reflection of light by the object.

Moreover, the time employed for colour observation, observer's experience, and type of shade guide, as well as the material's composition, are other subjective factors that critically influence the shade selection.

In general, shade guides for use in dentistry follow Munsell's colour parameters (Sproull, 2001), in which three dimensions are defined: hue (basic colour), chroma (saturation), and value (brightness).

In the case of direct restorations, employing resin composite shade guides, although recommended for the initial evaluation of colour, may be confusing and, despite several attempts to define a protocol for use, still rely on the clinical experience of the observer and the inoffice illumination.

Moreover, due to the optical phenomena occurring on natural teeth, it is necessary to select colours for dentine, enamel, and incisal translucent areas to obtain a better layering technique.

Over the past decade, there has been an increasing interest in illumination techniques for use in dental photography. Digital pictures can help minimise errors in clinical practice, especially during the shade matching of natural teeth. The protocol based on cross-polarisation, eliminating the superficial enamel light reflection, allows unobstructed visualisation of surface and subsurface enamel characteristics.

This technique enables easy and more accurate selection of the hue and chroma of the dentine (Bazos and Magne, 2011).

Moreover, as demonstrated, the use of polarising filters associated with digital photography is a simple and straightforward method for better understanding the colour of natural anterior teeth (Hein and Zangl, 2016).

For a better use of this resource, the authors recommend three pictures: the maxillary anterior teeth with a black background, the maxillary anterior teeth with a black background and the shade guide, and the maxillary anterior teeth with a black background and small portions of cured resin composites.

The first picture of this protocol enables the evaluation of the characteristics of both enamel and dentine, providing an understanding and estimation of how opaque each structure is.

The second picture is taken after the usual colour selection, employing shade guides, and serves to compare the general colour selected for the entire tooth with the estimated colour of the dentine.

The third picture is taken after selection of the specific resin composites for each layer and serves to check if the selection is appropriate.

It should be noted that not every resin composite system is equal, and, despite the shade specification made by each manufacturer, the colour itself may vary. This means that the A 1 dentine shade specified by one manufacturer may not correspond to the A 1 dentine shade specified by another.

Moreover, the shade selection using only shade guides may be misleading if custom-made shade guides produced with the actual resin composite are not used. For this reason, this third additional step will help the selection of the correct shade of a specific system.

In the present case report, in the evaluation of the colour of the sound central incisor with cross-polarised photography (Figure 6), the A 1 shade was selected with a shade guide originally designed for ceramics, which is not specific for the resin composite system used in the restoration.

For the specific resin composite system employed, after the application of the two opaques (ie, a first layer of a white opaque flowable resin composite and a second layer of a conventional opaque OP resin composite), the A 1 dentine shade would have an artificially bright effect instead of reaching the desired colour. Thus, A3 and A2 dentine shades were used to reproduce the colour variation of the dentine from cervical to incisal thirds.

Another interesting use of digital photography to help the clinician improve predictability when restoring discoloured teeth is the provisional application of a thin layer of an opaque resin composite after dental preparation followed by the evaluation of the change in brightness using greyscale

photographs (Fahl, 2007).

This technique can help reproduce the brightness (value) of the adjacent teeth and could be added to the photographic protocol proposed in the present case report. However, one should take care not to over-dehydrate dental tissues during restorative procedures, as brightness is elevated.

When taking digital photographs, the reflection of the flash on the enamel of the adjacent teeth may increase the brightness, especially when ring flashes are used. For this reason, twin flashes are better for taking pictures of anterior teeth.

Bouncers adapted to twin flashes are other interesting accessories that can modify tooth chromaticity (Hein and Zangl, 2006), as well as perceivable changes of brightness on the tooth. For this reason, their use is recommended, except for in cross-polarised photography.

As suggested in the present case, the use of cross-polarised photography to assess the chromaticity and brightness (value) should be done as soon as possible (ie, in a short time) during the restorative procedure due to the natural dehydration of teeth.

In addition, photographs with polarisation modalities can improve the evaluation of the level of brightness of resin composites and teeth when taken in greyscale because they remove the interferences of both environmental light and photographic equipment. interferences of both environmental light and photographic equipment.

Conclusions

The evaluation of hue, chroma, value, and colour characteristics exhibited by natural dentition using cross-polarisation may help achieve more predictable outcomes during the stratification technique with resin composites.

This study was conducted in accordance with all the provisions of the local human subjects oversight committee guidelines and policies of the Bauru School of Dentistry, University of Sao Paulo, Brazil.

The authors of this article certify that they have no proprietary, financial, or other personal interest of any nature or kind in any product, service, and/or company that is presented in this article. the local human subjects oversight committee guidelines and policies of the Bauru School of Dentistry, University of Sao Paulo, Brazil.

References

Bahannan SA (2014) Shade matching quality among dental students using visual and instrumental methods. *J Dent* 42(1): 48-52

Barber A, King P (2014a) Management of the single discoloured tooth. Part I: Aetiology, prevention and minimally invasive restorative options. *Dent Update* 41(2): 98-100, 102-104

Barber A, King P (2014b) Management of the single discoloured tooth. Part 2: Restorative options. *Dent Update* 41(3): 194-196, 198-200, 202-194

Bazos P, Magne P (2011) Bio-emulation: Biomimetically emulating nature utilizing a histoanatomic approach; structural analysis. *Eur J Est/Jet Dent* 6(1):8-19

Fahl N (2006) A polychromatic composite layering approach for solving a complex class IV/direct veneer diastema combination: Part I. *Pract Proced Aesthet Dent* 18(10): 641-645

Fahl N (2007) A polychromatic composite layering approach for solving a complex class IV/direct veneer/ diastema combination: Part II. *Pract Proced Aesthet Dent* 19(1) 17-22

Ferracane JL (2011) Resin composites - state of the art. *Dent Mater* 27(1): 29-38

Fleming CM, Beal J F, Levine RS (1989) Photographic technique for the recording of children's teeth for signs of enamel mottling. *J Audiov Media Med* 12(1): 16-18

Furuse AY, Soares JV, Cunali RS, Gonzaga CC (2016) Minimum intervention in restorative dentistry with V-shaped facial and palatal ceramic veneers: A clinical report. *J Prosthet Dent* 115(5): 527-530

Gomes G, Perdigao I (2014) Prefabricated composite resin veneers - a clinical review. *J Est/Jet Res Dent* 26(5): 302-313

Haddad HJ, Salameh Z, Sadig W, Aboushelib M, Jakstat HA (2011) Allocation of color space for different age groups using three-dimensional shade guide systems. *Eur J Est/Jet Dent* 6(1): 94-102

Hein S, Zangl M (2016) The use of a standardized gray reference card in dental photography to correct the effects of

five commonly used diffusers on the color of 40 extracted human teeth. *Int J Est/Jet Dent* 11 (2): 246-259

Joiner A (2004) Tooth colour: A review of the literature. *J Dent* 32(Suppl 1): 3-12

Kim E, Son T, Lee Y, Jung B (2012) Development of polarization dental imaging modality and evaluation of its clinical feasibility. *J Dent* 40(Suppl 1): e18-e25

Korkut B, Yarnkoglu F, Günday M (2013) Direct composite laminate veneers: Three case reports. *J Dent Res Dent Clin Dent Prospects* 7(2): 105-111

Paolone G, Orsini G, Manauta J, Devoto W, Putignano A (2014) Composite shade guides and color matching. *Int/J Est/Jet Dent* 9(2): 164-182

Pekarek D (1993) The use of cross-polarized illumination for patient photography. *Biol Photogr* 1(3): 95-97

Prevedello GC, Vieira M, Furuse AY, Correr GM, Gonzaga CC (2012) Esthetic rehabilitation of anterior discolored teeth with lithium disilicate allceramic restorations. *Gen Dent* 60(4): e274-e278

Reis A, Higashi C, Loguercio AD (2009) Reanatomization of anterior eroded teeth by stratification with direct composite resin. *J Est/Jet Res Dent* 21(5): 304-316

Sproull RC (2001) Color matching in dentistry. Part II. Practical applications of the organization of color. *J Prost/Jet Dent* 86(5): 458-464

Vanini L (1996) Light and color in anterior composite restorations. *Pract Peri odontology and Aesthet Dent* 8(7): 673-682

Zenthofer A, Viesberg S, Hildenbrandt A, Reinelt G, Rammelsberg P, Hassel AJ (2014) Selecting VITA classical shades with the VITA 3D-master shade guide. *Int/ Prost/Jodont* 27(4): 376-382

Reprinted with permission by ADT August 2018